

V.G. Grossman<sup>1</sup>, B.G. Bazarov<sup>1,2</sup>, Zh.G. Bazarova<sup>2</sup>

<sup>1</sup>*Baikal Institute of Nature Management,  
Siberian Branch of Russian Academy of Sciences,  
8 Sakh'yanovoi St., Ulan-Ude, 670047, Russian Federation  
e-mail: grossmanv@mail.ru*  
<sup>2</sup>*Buryat State University,  
24a SmolinaSt., Ulan-Ude, 670000, Russian Federation*

DOI: 10.15826/chimtech/2017.4.4.02

## Phase equilibria in the $Tl_2MoO_4-R_2(MoO_4)_3-Zr(MoO_4)_2$ (R = Al, Cr) systems: synthesis, structure and properties of new triple molybdates $Tl_5RZr(MoO_4)_6$ and $TlRZr_{0.5}(MoO_4)_3$

The  $Tl_2MoO_4-R_2(MoO_4)_3-Zr(MoO_4)_2$  (R = Al, Cr) systems were studied in the subsolidus region using X-ray powder diffraction and differential scanning calorimetric (DSC) analysis. Quasi-binary joins were revealed, and triangulation was carried out. New ternary molybdates  $Tl_5RZr(MoO_4)_6$  (5:1:2) and  $TlRZr_{0.5}(MoO_4)_3$  (1:1:1) (R = Al, Cr) were prepared. The unit cell parameters for the new compounds were calculated.

**Keywords:** phase equilibria, synthesis, systems, thallium, zirconium, iron, aluminum, crystal structure, space group.

Received: 23.10.2017; accepted: 01.12.2017; published: 25.12.2017.

© Grossman V.G., Bazarov B.G., Bazarova Zh.G., 2017

### Introduction

This paper is a continuation of our systematic studies of phase relations in the  $Tl_2MoO_4-R_2(MoO_4)_3-A(MoO_4)_2$  (R – trivalent metals, A = Zr, Hf) ternary salt systems [1]. Earlier we studied phase equilibria in the  $Tl_2MoO_4-Fe_2(MoO_4)_3-Hf(MoO_4)_2$  system [2]. Subsolidus phase diagrams for this system and constituent double systems were constructed, and triple molybdates  $Tl_5FeHf(MoO_4)_6$  and

$TlFeHf_{0.5}(MoO_4)_3$  had been detected. The aims of the present study include (1) investigation of phase equilibria in the ternary salt systems  $Tl_2MoO_4-R_2(MoO_4)_3-Zr(MoO_4)_2$  (R = Al, Cr), (2) determination of optimal condition for the solid state synthesis of ternary molybdates found in these systems, and (3) determination of crystallographic and thermal characteristics of the obtained compounds.

### Experimental

Subsolidus phase relations in the  $Tl_2MoO_4-R_2(MoO_4)_3-Zr(MoO_4)_2$  (R = Al, Cr) systems were studied in the subsolidus region (500–550 °C) using the intersecting joins method.

The corresponding molybdates of thallium, aluminum, chromium and zirconium were used as initial components for studying the phase equilibria in the  $Tl_2MoO_4-R_2(MoO_4)_3-Zr(MoO_4)_2$  (R = Al,

Cr) systems. Synthesis of  $Tl_2MoO_4$  was carried out according to the reaction  $Tl_2O_3 + MoO_3 \rightarrow Tl_2MoO_4 + O_2 \uparrow$  at gradually increasing temperature in the range 400–550 °C for 50 h. The high temperature modification of  $Zr(MoO_4)_2$  was prepared by annealing of stoichiometric mixture of binary oxides  $ZrO_2$  and  $MoO_3$  at 400–700 °C for 100 h. Aluminum molybdate and chromium molybdate were obtained by calcination of stoichiometric mixtures of precursors  $Al(NO_3)_3 \cdot 9H_2O$ ,  $Cr_2O_3$ , and  $MoO_3$  in the temperature range 400–650 °C for 100 h. The initial stage of each synthesis was chosen as 400 °C since  $MoO_3$  possesses high volatility at temperature about 600 °C. To ensure better homogenization, the reaction mixtures were ground in ethanol every 20–30 h during firing. After annealing, the samples were slowly cooled in the furnace. The non-

equilibrium samples were additionally annealed. It was assumed that equilibrium is reached if the phase composition of the samples remains unchanged during two consecutive anneals. The crystallographic parameters of the synthesized compounds were close to those reported in literature [3–5].

X-ray powder diffraction (XRD) measurements were performed using Bruker D8 Advance diffractometer (Bragg–Brentano geometry, Cu K $\alpha$  radiation, secondary monochromator, maximum angle  $2\theta=100^\circ$ , scan step  $0.02^\circ$ ). The differential scanning calorimetric (DSC) analysis of the samples was carried out using NETZCH STA 449C (Jupiter, Germany) thermoanalyzer. Compounds' pellets were placed in a Pt-crucible, heated up and then cooled down in argon atmosphere with the heating and cooling rate of 10 K/min.

## Results and discussion

The information about the phase formation in the  $Tl_2MoO_4$ – $R_2(MoO_4)_3$ – $Zr(MoO_4)_2$  (R = Al, Cr) systems, which represent the bounding sides of the studied system, were taken from previous papers [3–5]. The formation of double molybdates with general composition  $TlR(MoO_4)_2$  was detected in the boundary  $Tl_2MoO_4$ – $R_2(MoO_4)_3$  systems [3]. Two double molybdates  $Tl_8Zr(MoO_4)_6$  and  $Tl_2Zr(MoO_4)_3$  were formed in the  $Tl_2MoO_4$ – $Zr(MoO_4)_2$  system [4]. No intermediate compounds were found in the  $R_2(MoO_4)_3$ – $Zr(MoO_4)_2$  systems [5].

In order to find new triple molybdates, the subsolidus phase equilibria in the  $Tl_2MoO_4$ – $R_2(MoO_4)_3$ – $Zr(MoO_4)_2$  (R = Al, Cr) systems were studied at 500–550 °C and its triangulated phase diagrams were constructed. Solid-state interactions between  $Tl_2MoO_4$ ,  $R_2(MoO_4)_3$ , and

$Zr(MoO_4)_2$ , which occurred over wide ranges of temperature and concentration, led to the formation of new triple molybdates  $Tl_5RZr(MoO_4)_6$  (5:1:2 mole ratio)  $S_1$  and  $TlRZr_{0.5}(MoO_4)_3$  (1:1:1 mole ratio)  $S_2$ . Compound  $S_2$  was found at the intersection point of the  $R_2(MoO_4)_3$ – $Tl_2Zr(MoO_4)_3$  and  $TlR(MoO_4)_2$ – $Zr(MoO_4)_2$  joins. The triple molybdate ( $S_1$ ) locates inside the triangle with the double molybdates  $TlR(MoO_4)_2$ ,  $Tl_8Zr(MoO_4)_6$  and  $Tl_2Zr(MoO_4)_3$  in its vertices.

The phase relations in the  $Tl_2MoO_4$ – $R_2(MoO_4)_3$ – $Zr(MoO_4)_2$  (R = Al, Cr) systems are shown in Fig. 1.

Individual  $Tl_5RZr(MoO_4)_6$  (R = Al, Cr) oxides were prepared by firing at 450–550 °C for 150–200 h, and the molybdates  $TlRZr_{0.5}(MoO_4)_3$  (R = Al, Cr) were obtained by firing at temperatures from 500 to 600 °C for 100–150 h.

The single phase  $\text{Tl}_5\text{AlZr}(\text{MoO}_4)_6$  was not synthesized under the conditions of our experiment.

The analysis of X-ray diffraction patterns of the compounds obtained shows that the reflection positions and their intensity ratio for  $\text{TlRZr}_{0.5}(\text{MoO}_4)_3$  and  $\text{Tl}_5\text{RZr}(\text{MoO}_4)_6$  ( $\text{R} = \text{Al}, \text{Cr}$ ) are similar to  $\text{TlFeHf}_{0.5}(\text{MoO}_4)_3$  [2] and  $\text{Rb}_5\text{ErHf}(\text{MoO}_4)_6$  [6], respectively. It could be concluded that  $\text{TlRZr}_{0.5}(\text{MoO}_4)_3$  is isostructural to  $\text{TlFeHf}_{0.5}(\text{MoO}_4)_3$  and  $\text{Tl}_5\text{RZr}(\text{MoO}_4)_6$  is isostructural to  $\text{Rb}_5\text{ErHf}(\text{MoO}_4)_6$ .

Three dimensional framework of the  $\text{TlFeHf}_{0.5}(\text{MoO}_4)_3$  crystal structure ( $a = b = 13.0324(2) \text{ \AA}$ ,  $c = 11.8083(3) \text{ \AA}$ ,  $V = 1736.87(6) \text{ \AA}^3$ ,  $\rho_{\text{calc}} = 4.757 \text{ g/cm}^3$ , space group  $R\bar{3}$ ,  $Z = 6$ ) is composed of the  $\text{Mo}$ -tetrahedra sharing O vertices with the  $(\text{Fe}, \text{Hf})\text{O}_6$  octahedra, with thallium atoms occupying wide channels in the framework [2] (Figs. 2 and 3). The arrangement of Tl atoms (pink spheres) in the structural channel in  $\text{TlFeHf}_{0.5}(\text{MoO}_4)_3$  is shown in Fig. 3.

$\text{Rb}_5\text{ErHf}(\text{MoO}_4)_6$  possesses the trigonal crystal structure:  $a = 10.7511(1) \text{ \AA}$ ,  $c = 38.6543(7) \text{ \AA}$ ,  $V = 3869.31(9) \text{ \AA}^3$ ,  $\rho_{\text{calc}} = 4.462 \text{ g/cm}^3$ ,  $Z = 6$ , space group  $R\bar{3}c$  [6]. The three-dimensional framework of

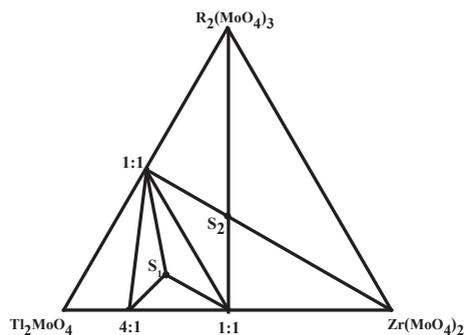


Fig. 1. Subsolidus phase relations in the  $\text{Tl}_2\text{MoO}_4\text{-R}_2(\text{MoO}_4)_3\text{-Zr}(\text{MoO}_4)_2$  ( $\text{R} = \text{Al}, \text{Cr}$ ) systems:  $\text{S}_1\text{-Tl}_5\text{RZr}(\text{MoO}_4)_6$  (5:1:2 mole ratio) and  $\text{S}_2\text{-TlRZr}_{0.5}(\text{MoO}_4)_3$  (1:1:1 mole ratio)

the structure is formed of the  $\text{MoO}_4$  tetrahedra, which are sharing corners with two  $\text{ErO}_6$  and  $\text{HfO}_6$  octahedra (Fig. 4). Two types of Rb atoms occupy large cavities in the framework. The particular ar-

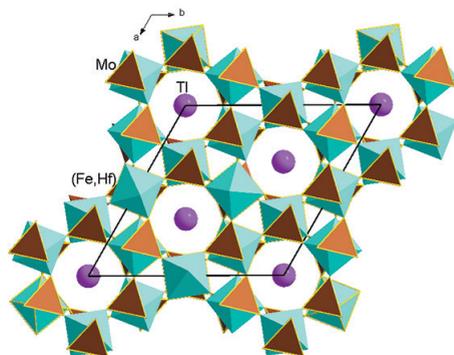


Fig. 2. The framework of  $\text{TlFeHf}_{0.5}(\text{MoO}_4)_3$  crystal structure that consists of  $\text{MoO}_4$  tetrahedra and  $(\text{Fe}, \text{Hf})\text{O}_6$  octahedra in the projection of layer onto the (001) plane (Tl atoms are represented by pink spheres)

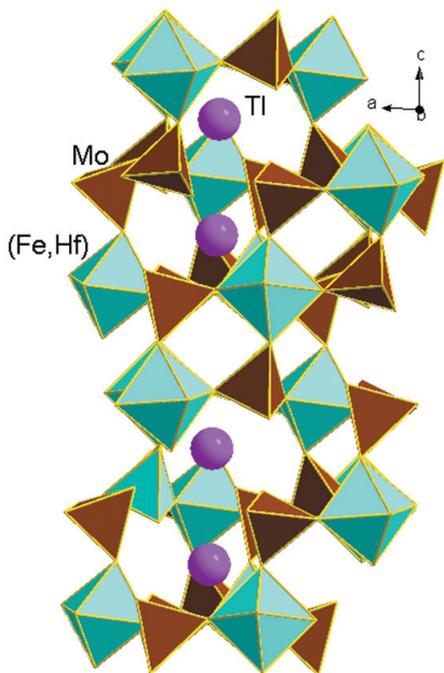


Fig. 3. The fragment of the  $\text{TlFeHf}_{0.5}(\text{MoO}_4)_3$  crystal structure that is projected onto the (010) plane

rangement of Rb atoms in the structural channel is shown in Fig. 5. The distribution of the  $\text{Er}^{3+}$  and  $\text{Hf}^{4+}$  cations over two positions is obtained during the structure refinement.

The unit cell parameters for the synthesized triple molybdates  $\text{TlRZr}_{0.5}(\text{MoO}_4)_3$  ( $\text{R} = \text{Al}, \text{Cr}$ ) were refined using uniquely-indexed lines for the  $\text{TlFeHf}_{0.5}(\text{MoO}_4)_3$  single crystal [2]. The lines for  $\text{Tl}_5\text{CrZr}(\text{MoO}_4)_6$  were indexed using  $\text{Rb}_5\text{ErHf}(\text{MoO}_4)_6$  [6] as analogous isostructural compound. The unit cell parameters that were refined using the TOPAS-4 software are listed in Table 1 along with the melting points of the corresponding compounds. Fig. 6 il-

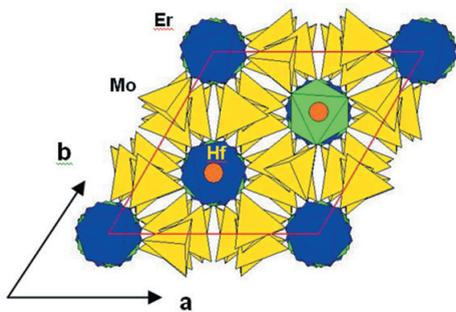


Fig. 4. Complex framework of the  $\text{Rb}_5\text{ErHf}(\text{MoO}_4)_6$  crystal structure built of the  $\text{MoO}_4$  tetrahedra and  $(\text{Er}, \text{Hf})\text{O}_6$  octahedra.

Red parallelogram shows the projection of a layer onto the (001) plane. The Rb atoms are represented by the orange spheres

lustrates good coincidence of the experimental and calculated profiles.

As shown in Table 1, the unit cell parameters and volume of  $\text{TlRZr}_{0.5}(\text{MoO}_4)_3$  ( $\text{R} = \text{Al}, \text{Cr}$ ) and  $\text{Tl}_5\text{CrZr}(\text{MoO}_4)_6$  increase with the substitution of 6-coordinated aluminum cations ( $r = 0.535 \text{ \AA}$ ) with a larger chromium cation ( $r = 0.615 \text{ \AA}$ ) [7]. The linear dependence of the unit cell volume on the trivalent element radii is also in accordance with  $\text{TlRZr}_{0.5}(\text{MoO}_4)_3$  ( $\text{R} = \text{Al},$


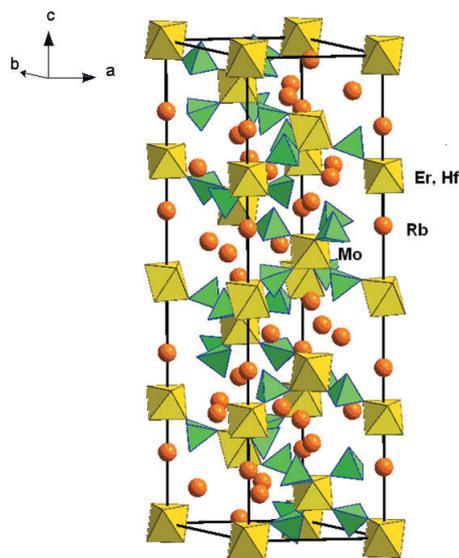


Fig. 5. Crystal structure of  $\text{Rb}_5\text{ErHf}(\text{MoO}_4)_6$  as projected on plane (133)


Table 1

The unit cell parameters and melting points of  $\text{TlRZr}_{0.5}(\text{MoO}_4)_3$  ( $\text{R} = \text{Al}, \text{Cr}$ ) and  $\text{Tl}_5\text{CrZr}(\text{MoO}_4)_6$  in comparison with literature data


Compound	Unit cell parameters ( $\text{\AA}$ )				$T, ^\circ\text{C}$
	$a, \text{\AA}$	$c, \text{\AA}$	$V, \text{\AA}^3$	space group; $Z$	
$\text{TlFeHf}_{0.5}(\text{MoO}_4)_3$ [2]	13.0324(2)	11.8083(3)	1736.87(6)	$R\bar{3}c; 6$	811
$\text{TlAlZr}_{0.5}(\text{MoO}_4)_3$	12.5935(6)	11.5946(8)	1592.5(2)		751
$\text{TlCrZr}_{0.5}(\text{MoO}_4)_3$	12.6961(6)	11.7022(9)	1633.6(2)		842
$\text{Rb}_5\text{ErHf}(\text{MoO}_4)_6$ [6]	10.7511(1)	38.6543(7)	3869.31(9)	$R\bar{3}c; 6$	730
$\text{Tl}_5\text{CrZr}(\text{MoO}_4)_6$	10.4047(8)	37.5322(3)	3518.8(6)		599

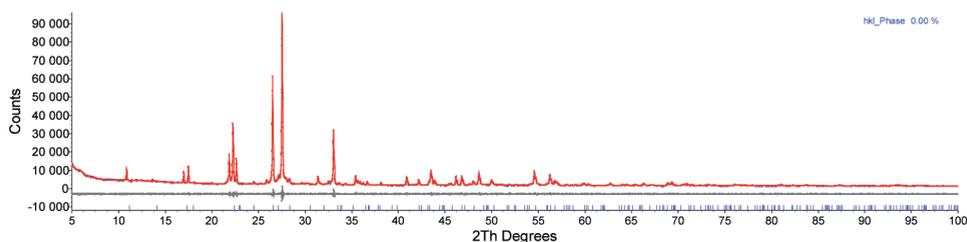

*a*

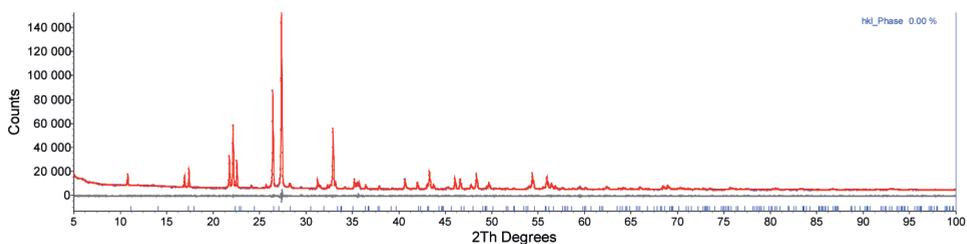

*b*

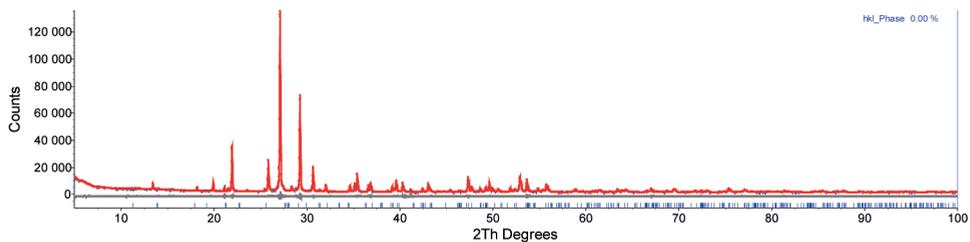

*c*

Fig. 6. Measured (red), calculated (black) and differential (blue) powder diffraction patterns for  $\text{TlCrZr}_{0.5}(\text{MoO}_4)_3$  (a),  $\text{TlAlZr}_{0.5}(\text{MoO}_4)_3$  (b) and  $\text{Tl}_5\text{CrZr}(\text{MoO}_4)_6$  (c)

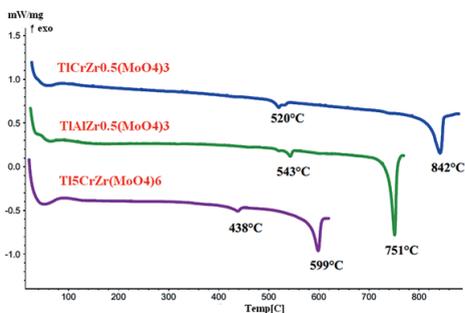


Fig. 7. DSC curves for  $\text{TlRZr}_{0.5}(\text{MoO}_4)_3$  ( $\text{R} = \text{Al}, \text{Cr}$ ) and  $\text{Tl}_5\text{CrZr}(\text{MoO}_4)_6$

## Conclusions

New triple molybdates with general compositions  $\text{Tl}_5\text{RZr}(\text{MoO}_4)_6$  (5:1:2) and  $\text{TlRZr}_{0.5}(\text{MoO}_4)_3$  (1:1:1) ( $\text{R} = \text{Al}, \text{Cr}$ ), respectively, were obtained in the thallium-

Cr) and  $\text{Tl}_5\text{CrZr}(\text{MoO}_4)_6$  belonging to one structural family.

Two endothermic effects are observed on the DSC curves (Fig. 7). The first one corresponds to some structural changes that, however, are not accompanied by the change of a structural type. The last endothermic effect corresponds to the melting of the studied compounds.

containing systems with trivalent metals and zirconium. The formation of these triple molybdates occurs similarly to the formation of ternary molybdate  $\text{Tl}(\text{FeHf}_{0.5})$

(MoO<sub>4</sub>)<sub>3</sub> in previously studied Tl<sub>2</sub>MoO<sub>4</sub>–Fe<sub>2</sub>(MoO<sub>4</sub>)<sub>3</sub>–Hf(MoO<sub>4</sub>)<sub>2</sub> system [2]. The phase relations do not change with haf-  
nium ( $r = 0.71 \text{ \AA}$ ) being substituted with zirconium ( $r = 0.72 \text{ \AA}$ ) [7].

## Acknowledgements

This work was carried out according to the state assignment BINM SB RAS (project no. 0339-2016-0007).

## References

1. Grossman VG, Bazarov BG, Bazarova ZhG. Subsolidus phase diagrams for the Tl<sub>2</sub>MoO<sub>4</sub>–Ln<sub>2</sub>(MoO<sub>4</sub>)<sub>3</sub>–Hf(MoO<sub>4</sub>)<sub>2</sub> systems, where Ln = La–Lu. *Russ J Inorg Chem.* 2008;53(11):1788–94. DOI:10.1134/S003602360811020X
2. Grossman VG, Bazarov BG, Klevtsova RF, Glinskaya LA, Bazarova ZhG. Phase equilibria in the Tl<sub>2</sub>MoO<sub>4</sub>–Fe<sub>2</sub>(MoO<sub>4</sub>)<sub>3</sub>–Hf(MoO<sub>4</sub>)<sub>2</sub> system and the crystal structure of ternary molybdate Tl(FeHf<sub>0.5</sub>)(MoO<sub>4</sub>)<sub>3</sub>. *Russ Chem Bull.* 2012;61(8):1546–9. DOI:10.1007/s11172-012-0202-7
3. Pleskov MY, Morozov VA, Lazoryak BI, Zhizhin MG, Burdakova IB, Khalbaeva KM, Tsyrenova GD, Khaikina EG. Structures of double molybdates TlR(MoO<sub>4</sub>)<sub>2</sub> (R = In, Sc, Fe, Cr, Al). *Russ J Inorg Chem.* 2005(4);50:604–14.
4. Bazarov BG, Klevtsova RF, Bazarova TsT, Glinskaya LA, Fedorov KN, Bazarova ZhG, Chimitova OD. Systems Tl<sub>2</sub>MoO<sub>4</sub>–E(MoO<sub>4</sub>)<sub>2</sub>, where E = Zr or Hf, and the crystal structure of Tl<sub>8</sub>Hf(MoO<sub>4</sub>)<sub>6</sub>. *Russ J Inorg Chem.* 2006;51(5):794–9. DOI:10.1134/S0036023606050184
5. Tushinova YuL, Bazarova ZhG, Archincheyeva SI. Abstracts of the reports. Ulan-Ude (Russia): Publishing house of BSC SB RAS; 2002. p. 90–1. Russian.
6. Bazarov BG, Klevtsova RF, Chimitova OD, Glinskaya LA, Fedorov KN, Tushinova YuL, Bazarova ZhG. Phase formation in the Rb<sub>2</sub>MoO<sub>4</sub>–Er<sub>2</sub>(MoO<sub>4</sub>)<sub>3</sub>–Hf(MoO<sub>4</sub>)<sub>2</sub> system and the crystal structure of new triple molybdate Rb<sub>5</sub>ErHf(MoO<sub>4</sub>)<sub>6</sub>. *Russ J Inorg Chem.* 2006;51(5):800–4. DOI:10.1134/S0036023606050196
7. Shannon RD. Revised effective ionic radii and systematic studies of interatomic distances in halides and chalcogenides. *Acta Cryst.* 1976;A32:751–67. DOI:10.1107/S0567739476001551

## Cite this article as:

Grossman VG, Bazarova BG, Bazarova ZhG. Phase equilibria in the Tl<sub>2</sub>MoO<sub>4</sub>–R<sub>2</sub>(MoO<sub>4</sub>)<sub>3</sub>–Zr(MoO<sub>4</sub>)<sub>2</sub> (R = Al, Cr) systems: synthesis, structure and properties of new triple molybdates Tl<sub>5</sub>RZr(MoO<sub>4</sub>)<sub>6</sub> and TlRZr<sub>0.5</sub>(MoO<sub>4</sub>)<sub>3</sub>. *Chimica Techno Acta.* 2017;4(4):218–23. DOI:10.15826/chimtech/2017.4.4.02.